

Development of a pH Dependent Colon Targeted Drug Delivery System for Mesalamine Delayed Release Tablets

Authors: Vaibhav Ambudkar¹, Hemant Bankhede¹, Shantanu Damle¹, Daniel To², Ali Rajabi Siahboomi²

¹Colorcon Asia. Pvt. Ltd. Verna, Goa, India, ²Colorcon Inc. Harleysville, PA, USA | AAPS Poster Reprint 2020

Introduction

Mesalamine (5-aminosalicylic acid, 5-ASA) is commonly used in the treatment of mild-to-moderate ulcerative colitis.¹ It acts locally on the colonic mucosa to achieve its therapeutic effect. However, if it is released in the upper gastrointestinal tract (GIT), it is rapidly and extensively absorbed in the small intestine which may lead to the less efficient delivery of the mesalamine in the colon, resulting in lower efficacy, along with significant systemic side effects.² To overcome these challenges pH-dependent enteric coating of solid oral dosage forms is commonly used for oral delivery of mesalamine to the colon. The pH of GIT increases progressively from stomach (pH 2.0 - 3.0), through small intestine (pH 6.5 - 7.0) to the colon (pH 7.0 - 8.0) based on physiological conditions.³

The purpose of this work was to investigate the use of fully formulated enteric coating systems to impart acid resistance to a mesalamine tablet formulation in pH 1.2 and pH 6.0, while achieving complete drug release at pH 7.2 as per the USP monograph of mesalamine delayed release (DR) tablets.

Methods


Core Tablet Manufacture

A high shear wet granulation (HSWG) process was used to granulate part of the formulation as shown in Table 1 and Figure 1. The lubricated blend was compressed on a rotary tablet press (Rimek, Mini Press II) using 19 × 9 mm plain, oval standard concave tablet tooling at a target weight of 1025 mg.

Table 1: Composition of Mesalamine Tablets, 800 mg

Ingredients	% W/W	mg/dosage
Intragranular		
Mesalamine USP	78.05	800.0
Sodium Starch glycolate Type A	3.51	36.0
MCC PH 102	5.06	52.0
PVP K30	4.09	42.0
Extragranular		
Starch 1500	5.07	52.0
Sodium Starch glycolate Type A	2.54	26.0
Colloidal Silicon Dioxide	0.58	6.0
Talc	0.56	5.8
Magnesium stearate	0.50	5.2
Total	100.0	1025.0

Figure 1: Flowchart for Manufacturing of Mesalamine Tablets

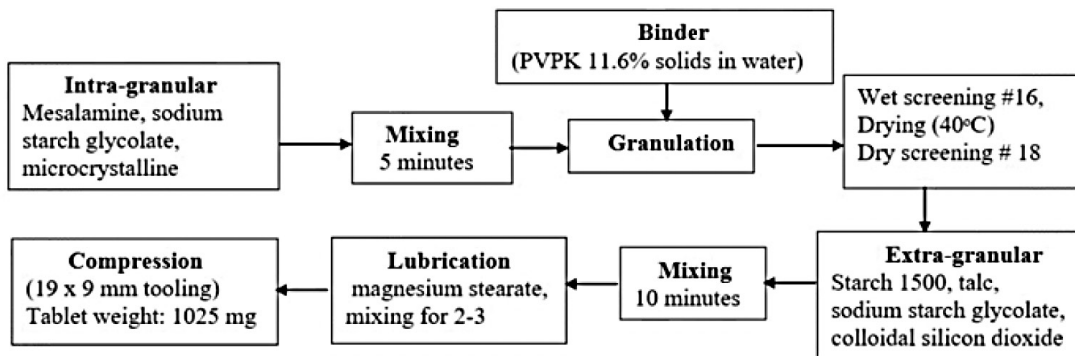

Coating of Tablets

Mesalamine tablets were seal-coated with an HPMC-based clear Opadry® complete film coating system to 3.5% weight gain using 10% w/w solids in water. The seal-coated tablets were subsequently enteric coated with Opadry Enteric using below sequential steps (Figure 2 and Table 2)

Step 1: Opadry Enteric 95K (dissolution trigger pH > 7.0) to a weight gain of 3% using 10% w/w solids in IPA: Water (88:12 by weight).

Step 2: Opadry Enteric 940 (dissolution trigger pH > 6.0) to a weight gain of 3% using 10% w/w solids in IPA: Water (88:12 by weight).

Table 2: Coating Process Parameters

Parameter	Seal-coat	Enteric coat Step 1 (95K)	Enteric coat Step 2 (940)
Tablet load (kg)	1	1	1
Weight gain (% w/w)	3.5	3	3
Atomization air pressure (bar)	1.2 – 1.3	0.5 – 0.7	0.5 – 0.7
Pattern air pressure (bar)	1.2 – 1.3	0.5 – 0.7	0.5 – 0.7
Pan speed (rpm)	9	9	9
Inlet air temperature (°C)	58 – 61	31 – 32	31 – 32
Exhaust air temperature (°C)	44 – 47	29 – 31	29 – 31
Bed temperature (°C)	44 – 46	29 – 30	29 – 30
Air volume (m ³ /hr)	107	115	113
Spray rate (gm/min)	2 – 4	2 – 4	2 – 4

Figure 2: Coating Layers and Appearances of Tablet (Core vs. Coated)



Enteric Performance Testing

Enteric protection performance of coated tablets (n=6) was evaluated using a USP disintegration bath (Electrolab, ED-2L) containing 0.1 N HCl for 2 hours; followed by buffer stage I with phosphate buffer pH 6.0 for 1 hour at $37 \pm 2^\circ\text{C}$ and media uptake calculated as % of initial weight. The intact tablets were then reciprocated in the disintegration apparatus using pH 7.2 phosphate buffer (buffer Stage II), at 37.0°C . The time taken for all the tablets to disintegrate completely was recorded. Buffer stage medium 1 and 2 were prepared as per USP general chapter "Buffer Solutions".

Assay, Impurities and Dissolution

Drug assay and impurities testing was performed per the USP monograph for mesalamine delayed release tablets. Dissolution testing was carried out per the USP monograph for mesalamine delayed release tablets (n=6). Drug release was determined using a USP dissolution bath (Electrolab, EDT-08LX) using the following dissolution media sequence at 37.0 ± 0.5

Drug Release Testing

Dissolution testing was carried out per the USP monograph for mesalamine delayed release tablets (n=6). Drug release

was determined using a USP dissolution bath (Electrolab, EDT-08LX) using the following dissolution media sequence at $37.0 \pm 0.5^\circ\text{C}$.

1. Acid Stage: 500 mL of 0.1M HCl, Apparatus II at 100 rpm for 120 min,
2. Buffer Stage I: 900 mL of phosphate buffer pH 6.0, Apparatus II at 100 rpm for 60 min
3. Buffer Stage II: 900 mL of phosphate buffer pH 7.2, Apparatus II at 50 rpm for 90 min

At the end of the acid stage, (120 min) and buffer stage I (60 min), an aliquot was taken and tested for % mesalamine released. Further dissolution testing was continued with buffer stage II and sample aliquots were withdrawn at 15, 30, 60, and 90 min and analyzed for the amount of mesalamine released.

Stability Testing

Coated tablets were packaged in 100 cc HDPE bottles (Shriji Polymers, India), and stored at $30^\circ\text{C}/65\% \text{RH}$ and $40^\circ\text{C}/75\% \text{RH}$ for 1, 3 and 6 months. Stability was monitored by testing drug release, assay, impurities, liquid uptake as described above, and disintegration time of enteric coated tablets.

Results

Testing of Physical Properties of Tablets

The physical parameters for the compressed tablets are summarized in Table 3.

Table 3: Physical Properties of Mesalamine Core Tablets

Test	Result
Tablet weight (mg)	1026.8 ± 1.13
Tablet Width (mm)	9.02 ± 0.0
Tablet thickness (mm)	7.2 ± 0.01
Length (mm)	19.04 ± 0.01
Disintegration time (min)	3 - 4
Hardness (kPa)	13.7 ± 0.8
Friability (%)	0.08

Enteric Performance Test

Enteric performance test showed that mesalamine tablets remained intact during the acid stage (0.1 M HCl) and buffer

stage I (buffer pH 6.0) indicating low liquid uptake (less than 5%) followed by rapid disintegration in buffer stage II (buffer pH 7.2) (Table 4).

Table 4: Assessment of Enteric Performance Test with Liquid Uptake in 0.1 N HCl and Buffer Stage 1

Media	Observations
Acid stage (0.1 M HCl); 2h	All Tablets intact Acid uptake (%): 2.1 to 2.7
Buffer Stage I (pH 6.0); 1h	All Tablets intact Acid uptake (%): 2.5 to 4.0
Buffer Stage II (pH 7.2)	All tablets disintegrated in 32 to 52 min

Assay and Impurities

The assay content and total impurities for mesalamine tablets were 102.0% and 0.012% (t_0), respectively (Table 5).

Table 5: Assay and Impurities Test Result


Test	Result	Limit
Assay (%)	102.0	90-110
Impurities		
Salicylic acid (%)	0	NMT 1.0
3-amino salicylic acid (%)	0	NMT 1.0
Total impurities (%)	0.0121	NMT 2.0

Drug Release Test

Mesalamine tablets complied with the dissolution test for all media sequences. Results indicated that the drug loss was

<1% at the end of 3 hours, 2 hours in the acid media (0.1N HCl) and 1 hour in the buffer stage I. This was followed by a rapid release of drug in phosphate buffer, pH 7.2 (Figure 3).

Figure 3: Release from Mesalamine DR tablets, 800 mg coated with Opadry Enteric Systems

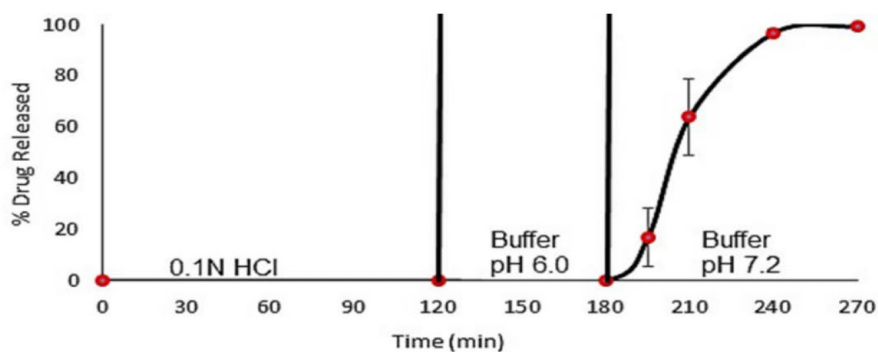

Stability Testing

The results of accelerated stability studies at 1, 3 and 6 months showed no significant change in enteric performance (Table 6), assay content, total impurities

(Table 7) and release profiles (Figure 4) regardless of storage conditions, confirming that the final dosage forms were stable in accelerated conditions.


Table 6: Enteric Performance Over Stability Conditions of 40°C/75% RH and 30°C/65% RH

Media	T0 / Initial	40°C/75% RH	30°C/65% RH
Acid stage (0.1 M HCl); 2 hr	2.1 to 2.7%	2.0 to 2.7%	2.1 to 2.74%
Buffer stage 1 (pH 6.0); 1 hr	2.5 to 4.0%	3.0 to 4.9%	3.1 to 3.7%
Buffer stage 2 (pH 7.2)	32 to 51 min	29 to 51 min	33 to 57 min

Table 7: Assay and Impurities Test Result at 30°C/65% RH and 40°C/75% RH

Media	T0 / Initial	40°C/75% RH	30°C/65% RH
Assay (%)	102.0	103.1	99.8
Salicylic acid (%)	0	0.01	0.01
3-amino salicylic acid (%)	0	0	0
Total impurities (%)	0.012	0.033	0.0169

Figure 4: Dissolution Profile of Mesalamine DR Tablets Over Stability

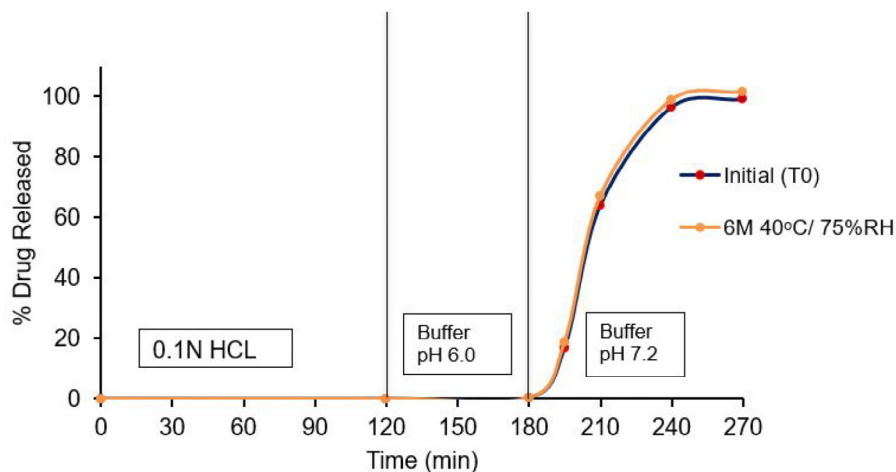

Conclusions

Opadry Enteric 95K (Step1) followed by Opadry Enteric 940 (Step 2) offered excellent enteric protection in both 0.1 M HCl and pH 6.0 buffer. Complete drug release was observed in phosphate buffer, pH 7.2 for mesalamine tablets (800 mg), which remained stable over the period of 6 months at accelerated storage conditions. These results show that Opadry Enteric 95K and 940 can be successfully used to achieve colon targeted delivery of drugs.

References

1. Lichtenstein GR, Kamm MA. Review article: 5-aminosalicylate formulations for the treatment of ulcerative colitis-methods of comparing release rates and delivery of 5-aminosalicylate to the colonic mucosa. *Aliment Pharmacol Ther.* 2008;28:663-73.2
2. Dhaneshwar SS, Chail M, Patil M, Naqvi S, Vadnerkar G. Colon specific mutual amide prodrugs of 4-aminosalicylic acid for their mitigating effect on experimental colitis in rats. *Eur J Med Chem.* 2009;44:131-42.
3. M. Ashford, T. Fell, Targeting drugs to the colon; delivery systems for oral administration, *J. Drug Targeting* 2 (1994) 241-258.

The information contained herein, to the best of Colorcon, Inc.'s knowledge is true and accurate. Any recommendations or suggestions of Colorcon, Inc. with regard to the products provided by Colorcon, Inc. are made without warranty, either implied or expressed, because of the variations in methods, conditions and equipment which may be used in commercially processing the products, and no such warranties are made for the suitability of the products for any applications that you may have disclosed. Colorcon, Inc. shall not be liable for loss of profit or for incidental, special or consequential loss or damages.

Colorcon, Inc. makes no warranty, either expressed or implied, that the use of the products provided by Colorcon, Inc., will not infringe any trademark, trade, copyright, patent or other rights held by any third person or entity when used in the customer's application.

For more information, contact your Colorcon representative or call:

North America	Europe/Middle East/Africa	Latin America	India	China
+1-215-699-7733	+44-(0)-1322-293000	+54-1-5556-7700	+91-832-6727373	86-21-61982300

You can also visit our website at www.colorcon.com